

GHGT-9

# Performance of a NiO-based oxygen carrier for chemical looping combustion and reforming in a 120kW unit

Johannes Bolhàr-Nordenkampf\*, Tobias Pröll, Philipp Kolbitsch, Hermann Hofbauer

*Vienna University of Technology, Getreidemarkt 9/166, Vienna 1060, Austria*

**Elsevier use only:** Received date here; revised date here; accepted date here

---

## Abstract

In this study the performance of two different Ni-based oxygen carriers in a 120kW chemical looping pilot rig at Vienna University of Technology is presented. A dual circulating fluidized bed (DCFB) system has been designed with the important characteristics of high solid circulation, very low residence times and a high power to solid inventory ratio. For all presented results the pilot rig is fueled with methane at 140kW fuel power. For both oxygen carriers high CH<sub>4</sub> conversion and CO<sub>2</sub> yield is achieved. Air to fuel ratio and temperature are varied. CH<sub>4</sub> conversion at higher air to fuel ratio as well as at higher temperature seems to decrease. This phenomenon is linked to the Ni/NiO ratio of the particle which determines the catalytic activity and thus influences the CH<sub>4</sub> conversion and the CO<sub>2</sub> yield.

© 2008 Elsevier Ltd. All rights reserved

*Keywords:* Chemical Looping; Oxygen Carrier; Gas-Solid Reactor; Fluidized Bed System; Nickel oxide

---

## 1. Introduction

Chemical looping combustion (CLC) and reforming (CLR) are novel fuel conversion technologies allowing inherent CO<sub>2</sub> separation. The main advantage of chemical looping for carbon capture is that there is no gas separation step needed to get a concentrated CO<sub>2</sub> stream. This includes that the energy penalty paid for carbon capture is systematically lower than for pre- or post combustion capture or for oxyfuel combustion. The technology was introduced by Richter and Knoche [1] and Ishida et al. [2] to increase the reversibility of combustion processes. Chemical looping systems consist of two reaction zones in which different gas streams are in contact with circulating solids. The circulating solid transports oxygen and heat from one reaction zone to the other. Metal oxides allow such a transport. In the fuel converting zone, fuel is oxidized by the metal oxide. This reaction zone is called fuel reactor (FR). In the second zone, called air reactor (AR), the metal oxide is reoxidized. Figure 1 shows a setup of chemical looping system. The inlet gases in the two reaction zones are not mixed and solid circulates between them to transport oxygen and heat. A chemical looping system can be operated either as a combustor or as a reformer.

---

\* Corresponding author. Tel.: +43 1 58801 15933; fax: +43 1 58801 15999.

E-mail address: [johannes.bolhar-nordenkampf@tuwien.ac.at](mailto:johannes.bolhar-nordenkampf@tuwien.ac.at)


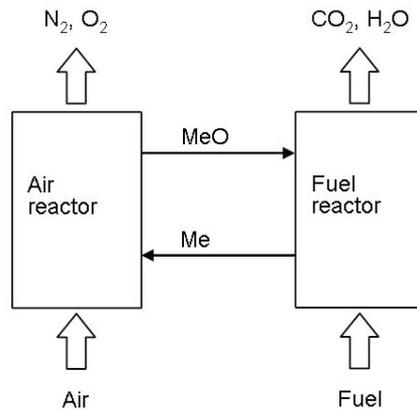


Figure 1. The chemical looping principle

If hydrocarbons are used as fuel in CLC, the main components of the FR exhaust gas are CO<sub>2</sub> and H<sub>2</sub>O. After condensation of water, a relatively pure CO<sub>2</sub> stream is left. Therefore this technology has a high potential for CO<sub>2</sub> separation. The AR exhaust gas consists mainly of nitrogen with some excess oxygen.

The global reactions for gaseous fuels are:

fuel reactor



air reactor



The AR reaction is exothermic whereas the FR reaction can be exothermic or endothermic. This depends on the fuel and the used oxygen carrier (OC). In the case of Ni-based OC and CH<sub>4</sub> as fuel the AR has an exothermic reaction but an endothermic FR reaction. The total heat release of the system is equal to the heat release of the direct combustion with air. [3]

The characteristic of the gas solid reaction in the FR and AR are

- enough residence time in the reaction zones,
- good gas solids mixing and
- an adequate OC for the used fuel.

At the pilot rig used within the present study, both reactors are designed as circulating fluidized beds with a direct hydraulic link at the bottom. The system is described in detail by Kolbitsch et al. [4].

## 2. General aspects of oxygen carriers

The basic requirements for OC are mechanical stability, lowest possible costs and high oxygen transport capacity. According to the used fuel the OCs has to fulfill other requirements. For hydrocarbon fuel a high catalytic activity is beneficial (especially for natural gas, i.e. methane). Ni- based carriers have a good catalytic activity and are suitable for methane combustion and reforming. Other possible metals beside Ni are: Cu, Fe, Co, Mn and Cd [5-16]. Most oxides have to be supported by other inert materials to gain the necessary strength and attrition stability to be operated in a CFB. Such support materials can be  $\text{Al}_2\text{O}_3$ ,  $\text{TiO}_2$ , yttria-stabilized zirconium or  $\text{MgO}$  [17].

In the present study, highly active carriers manufactured by VITO, Belgium under the guidance of Chalmers University of Technology, Sweden are used. The oxygen carrier A (OC-A) is based on NiO and  $\alpha\text{-Al}_2\text{O}_3$ . After sintering the particles consist of NiO and inert  $\text{NiAl}_2\text{O}_3$  [18]. The basic components of the second Ni-based oxygen carrier (OC-B) are NiO,  $\alpha\text{-Al}_2\text{O}_3$  and MgO. These particles are also sintered. More information can be found in the article by Jerndal et al. [18]. The mean particle size of both OCs is approximately 120  $\mu\text{m}$ .

## 3. The DCFB pilot rig

The chemical looping pilot rig is a DCFB system for gaseous fuels. The pilot rig is designed with respect to the typical properties of large scale installations. The nominal power of the pilot rig is 120kW with natural gas as the fuel. Alternatively,  $\text{H}_2$ , CO and  $\text{C}_3\text{H}_8$  can be used as fuel. Loop seals between the reactors avoid mixing of AR and FR gases. These loop seals are fluidized with superheated steam. The flow regime in the AR is fast fluidization and in the FR turbulent fluidization. Downstream of each reactor, gas and solids are separated in cyclone separators. A principle setup is shown in Figure 2.

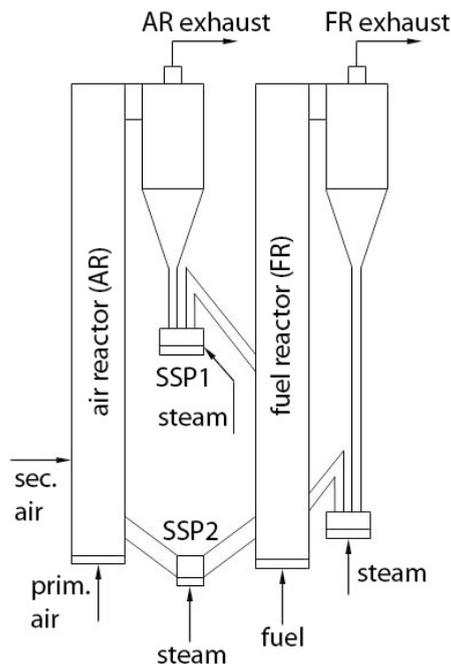


Figure 2 Principle setup of the DCFB reactor system

Depending on the different operating parameter (T, air/fuel ratio, fuel, etc.) of the chemical looping system, the pilot rig has to be cooled (Figure 3).

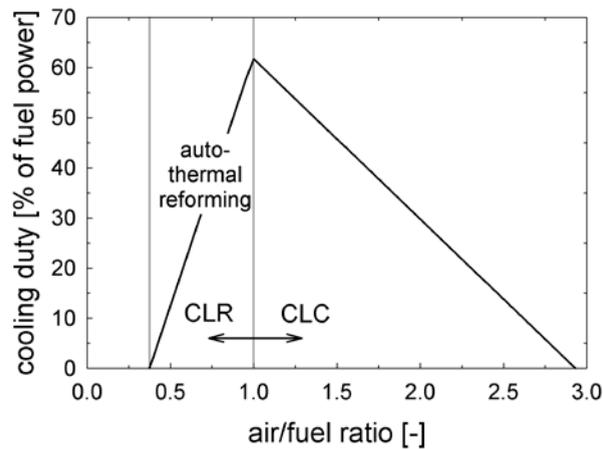


Figure 3 Theoretical cooling duty as a function of air/fuel ratio in case of full conversion to equilibrium [4]

A variable cooling system, consisting of three double jackets, is attached to the AR. A detailed description of the cooling system and the other auxiliary units can be found in Kolbitsch et al. [4].

The 120kW chemical looping pilot rig has been successfully operated since January 2008 at Vienna University of Technology. For the start up of the pilot rig a natural ore (ilmenite  $\text{FeTiO}_3$ ) was used. These first results are presented in other contributions to this conference [19, 20]. The present study focuses on the Ni-based particles, for which the pilot rig has actually been designed for.

In order to characterize the performance of the chemical looping system, the fuel conversion in terms of  $\text{CH}_4$  and the yield of  $\text{CO}_2$  based on total carbon supplied are used:

$$X_{\text{CH}_4} = \frac{y_{\text{CO}} + y_{\text{CO}_2}}{y_{\text{CO}} + y_{\text{CO}_2} + y_{\text{CH}_4}} \Bigg|_{\text{FRout}} \quad (6)$$

$$\gamma_{\text{CO}_2} = \frac{y_{\text{CO}_2}}{y_{\text{CO}} + y_{\text{CO}_2} + y_{\text{CH}_4}} \Bigg|_{\text{FRout}} \quad (7)$$

In these definitions, the  $y_i$  are mole fractions of the gas species measured in the FR exhaust stream.

#### 4. Operation results

The performance of the NiO-carriers (OC-A & OC-B) is demonstrated at the 120 kW pilot rig. Temperature and global air to fuel ratio are varied. The results shown in Figure 4 and Figure 5 are performed at 900°C, at an average fuel load of 140kW CH<sub>4</sub> and a total solids inventory of 65kg.

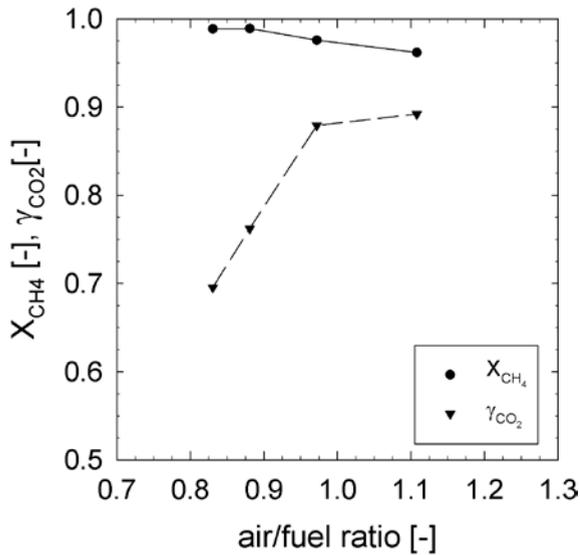


Figure 4 OC-A: CH<sub>4</sub> conversion and CO<sub>2</sub> yield vs. air to fuel ratio

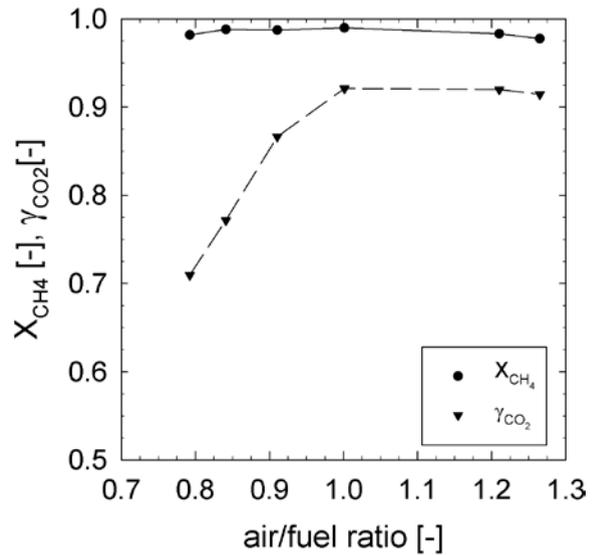
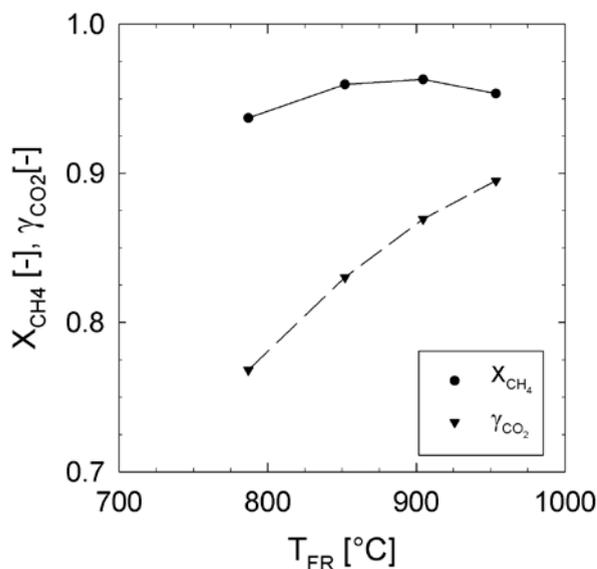
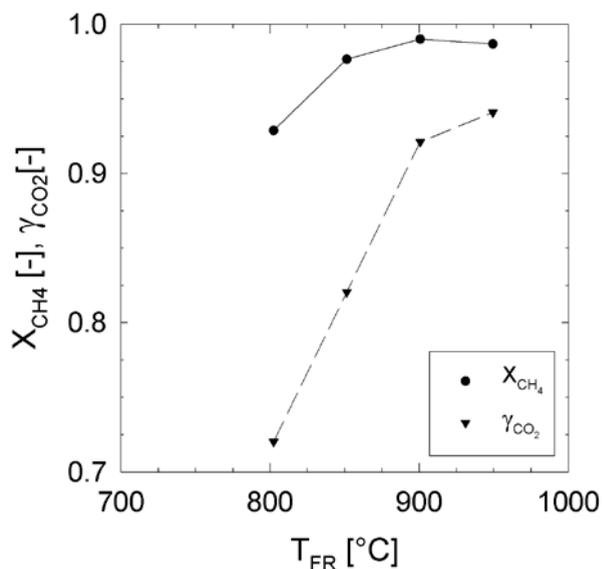


Figure 5 OC-B: CH<sub>4</sub> conversion and CO<sub>2</sub> yield vs. air to fuel ratio

The CH<sub>4</sub> conversion is high for both OCs but decreases with higher air to fuel ratio. This phenomenon seems to be linked to the Ni/NiO ratio in the particle [21]. With increasing air/fuel ratio the Ni/NiO ratio decreases. This seems to limit the catalytic activity of the OC and leads to the decrease in CH<sub>4</sub> conversion. With OC-B, which was optimized for high CH<sub>4</sub> conversion, this phenomenon is less pronounced. The CO<sub>2</sub> yield at global air/fuel ratios below one is limited mainly by the availability of oxygen. At an air/fuel ratio of one, the steep increase of the CO<sub>2</sub> yield flattens significantly for both OCs. There are different constraints in the pilot rig, which limit the CO<sub>2</sub> yield for global air/fuel ratios above one:

1. A low mean oxidation state of the OC entering the fuel reactor [21], which is welcome for good CH<sub>4</sub> conversion, limits the CO<sub>2</sub> yield.
2. The reactor height which limits the gas-solids contact time in the reactors (this could not be increased due to limiting laboratory height).
3. A relatively high solids circulation rate causes the age distribution of the particles in the reactors to be very narrow compared to other installations with lower circulation rates and higher specific solids hold up. This leads to a pronounced trade-off between satisfactory CH<sub>4</sub> conversion and high CO<sub>2</sub> yield.

Figure 6 OC-A: CH<sub>4</sub> conversion and CO<sub>2</sub> yield vs. FR temperatureFigure 7 OC-B: CH<sub>4</sub> conversion and CO<sub>2</sub> yield vs. FR temperature

Figures 6 and 7 demonstrate the influence of the FR temperature on the CH<sub>4</sub> conversion and the CO<sub>2</sub> yield. In both cases, Figures 6 for OC-A and Figure 7 for OC-B, the pilot rig is operated at a fuel load of 140kW CH<sub>4</sub> and an air/fuel ratio of approximately 1.10. In general the conversion becomes better with high temperature. The absolute numbers are higher for OC-B compared to OC-A. The CH<sub>4</sub> conversion shows a maximum around 900°C. This can be explained by the increasing degree of oxidation of the oxygen carrier particles with increasing temperature. The CO<sub>2</sub> yield increases over the whole temperature range. Possible reasons are increased reactivity and improved fluid dynamic regime in the fuel reactor.

## 5. Conclusion

More than 90 hours of CLC and CLR operation experience with Ni-based OC at different bed inventories have been reached at a 120 kW test rig. The unit can be fueled with CH<sub>4</sub>, CO, H<sub>2</sub>, C<sub>3</sub>H<sub>8</sub> or mixtures of these gases and can be operated with different oxygen carriers. The pilot rig design allows high solids circulation, low solids inventories and low solids residence time. The DCFB reactor system has a high potential for scale up. Therefore, the results obtained can be assigned to large plants to some extent. Two Ni-based OCs are compared and discussed for CH<sub>4</sub> fueled operation. These particles achieve high CH<sub>4</sub> conversion and high CO<sub>2</sub> yield. For high air/fuel ratio and high temperature the CH<sub>4</sub> conversion decreases. This is most likely caused by reduced catalytic activity due to reduced presence of metallic nickel at the surfaces of more oxidized particles. The CO<sub>2</sub> yield increases over the investigated temperature range and with increasing air/fuel ratio. This phenomenon is also linked to the Ni/NiO ratio of the particles and has some relevance for larger scale CLC units, where high circulation rates and low solids inventories may reduce operating costs. Further investigation of the observed trade-off between CH<sub>4</sub> conversion and CO<sub>2</sub> yield is surely required.

## Acknowledgements

This work was part of the EU financed project CLC GAS POWER (FP6 Contract No. 019800), coordinated by Chalmers University of Technology. The project is also part of phase II of CCP (CO<sub>2</sub> Capture Project) via Shell.

## References

1. H. Richter, K.F. Knoche, Reversibility of combustion processes, ACS Symposium Series 235 (1983), pp. 71 – 85.
2. M. Ishida, D. Zheng, T. Akehata, Evaluation of a chemical-looping combustion power-generation system by graphic exergy analysis, Energy 12 (1987), pp. 147 – 154.
3. A. Abad, F. Garc a-Labiano, J. Ad anez, L.F. de Diego, P. Gay an, J. Celaya, Applicability limits of Cu-, Fe-, and Ni-based oxygen carriers in chemical-looping combustion. 8th International conference on greenhouse gas control technologies, Trondheim, Norway (2006)
4. P. Kolbitsch, T. Pr oll, J. Bolhar-Nordenkampff, H. Hofbauer, Design of a chemical looping combustor using a dual circulating fluidized bed (DCFB) reactor system, Submitted to Chemical Engineering & Technology, Hamburg, Germany, (2008)
5. A. Abad, J. Adanez, F. Garcia-Labiano, L.F. de Diego, P. Gayan and J. Celaya, Mapping of the range of operational conditions for Cu-, Fe-, and Ni-based oxygen carriers in chemical-looping combustion, Chem. Eng. Sci. 62 (2007) 533.
6. F. Garcia-Labiano, J. Adanez, L.F. de Diego, P. Gayan and A. Abad, Effect of pressure on the behavior of copper-, iron-, and nickel-based oxygen carriers for chemical-looping combustion, Energy Fuels 20 (2006) 26.
7. M. Johansson, T. Mattisson and A. Lyngfelt, Use of NiO/NiAl<sub>2</sub>O<sub>4</sub> particles in a 10kW chemical-looping combustor, Ind. Eng. Chem. Res. 45 (2006) 5911.
8. T. Mattisson, M. Johansson and A. Lyngfelt, The use of NiO as an oxygen carrier in chemical-looping combustion, Fuel 85 (2006) 736.
9. S.R. Son and S.D. Kim, Chemical-looping combustion with NiO and Fe<sub>2</sub>O<sub>3</sub> in a thermobalance and circulating fluidized bed reactor with double loops, Ind. Eng. Chem. Res. 45 (2006) 2689.
10. Abad, T. Mattisson, A. Lyngfelt and M. Johansson, The use of iron oxide as oxygen carrier in a chemical-looping reactor, Fuel 86 (2007) 1021.
11. B.M. Corbella and J.M. Palacios, Titania-supported iron oxide as oxygen carrier for chemical-looping combustion of methane, Fuel 86 (2007) 113.
12. M. Ishida, K. Takeshita, K. Suuki and T. Ohba, Application of Fe<sub>2</sub>O<sub>3</sub>-Al<sub>2</sub>O<sub>3</sub> composite particles as solid looping material of the chemical-loop combustor, Energy Fuels 19 (2005) 2514.
13. M. Johansson, T. Mattisson and A. Lyngfelt, Investigation of Fe<sub>2</sub>O<sub>3</sub> with MgAl<sub>2</sub>O<sub>4</sub> for chemical-looping combustion, Ind. Eng. Chem. Res. 43 (2004) 6978.
14. L.F. de Diego, P. Gayan, F. Garcia-Labiano, J. Celaya, A. Abad and J. Adanez, Impregnated CuO/Al<sub>2</sub>O<sub>3</sub> oxygen carriers for chemical-looping combustion: Avoiding fluidized bed agglomeration, Energy Fuels 19 (2005) 1850.
15. F. Garcia-Labiano, L.F. de Diego, J. Adanez, A. Abad and P. Gayan, Reduction and oxidation kinetics of a copper-based oxygen carrier prepared by impregnation for chemical-looping combustion, Ind. Eng. Chem. Res. 43 (2004) 8168.
16. Abad, T. Mattisson, A. Lyngfelt and M. Ryden, Chemical-looping combustion in a 300W continuously operating reactor system using a manganese-based oxygen carrier, Fuel 85 (2006) 1174.
17. Lyngfelt A., Leckner B., Mattisson T. A fluidized-bed combustion process with inherent CO<sub>2</sub> separation; application of chemical-looping combustion. Chem. Eng. Sci. 56 (2001), pp. 3101 – 3113.
18. E. Jerndal, I. Thijsb, F. Snijkers, T. Mattisson, A. Lyngfelt, NiO particles with Ca and Mg based additives produced by spraydrying as oxygen carriers for chemical-looping combustion, 9<sup>th</sup> International Conference on Greenhouse Gas Technologies, Washington DC, US, 2008.
19. T. Pr oll, P. Kolbitsch, J. Bolhar-Nordenkampff and H. Hofbauer, Natural minerals as oxygen carriers for chemical looping combustion in a dual circulating fluidized bed system, 9<sup>th</sup> International Conference on Greenhouse Gas Technologies, Washington DC, US, 2008.
20. P. Kolbitsch, T. Pr oll, J. Bolhar-Nordenkampff, H. Hofbauer, Operating experience with chemical looping combustion in a 120kW dual circulating fluidized bed (DCFB) unit, 9<sup>th</sup> International Conference on Greenhouse Gas Technologies, Washington DC, US, 2008.
21. P. Kolbitsch, T. Pr oll, J. Bolhar-Nordenkampff and H. Hofbauer, Characterization of chemical looping pilot plant performance via experimental determination of solids conversion, submitted to Energy Fuels.